

# UNCLASSIFIED

# AD 102198

## Armed Services Technical Information Agency

Reproduced by

**DOCUMENT SERVICE CENTER**

**KNOTT BUILDING, DAYTON, 2, OHIO**

This document is the property of the United States Government. It is furnished for the duration of the contract and shall be returned when no longer required, or upon recall by ASTIA to the following address: Armed Services Technical Information Agency, Document Service Center, Knott Building, Dayton 2, Ohio.

**NOTICE: WHEN GOVERNMENT OR OTHER DRAWINGS, SPECIFICATIONS OR OTHER DATA ARE USED FOR ANY PURPOSE OTHER THAN IN CONNECTION WITH A DEFINITELY RELATED GOVERNMENT PROCUREMENT OPERATION, THE U. S. GOVERNMENT THEREBY INCURS NO RESPONSIBILITY, NOR ANY OBLIGATION WHATSOEVER; AND THE FACT THAT THE GOVERNMENT MAY HAVE FORMULATED, FURNISHED, OR IN ANY WAY SUPPLIED THE SAID DRAWINGS, SPECIFICATIONS, OR OTHER DATA IS NOT TO BE REGARDED BY IMPLICATION OR OTHERWISE AS IN ANY MANNER LICENSING THE HOLDER OR ANY OTHER PERSON OR CORPORATION, OR CONVEYING ANY RIGHTS OR PERMISSION TO MANUFACTURE, USE OR SELL ANY PATENTED INVENTION THAT MAY IN ANY WAY BE RELATED THERETO.**

# UNCLASSIFIED

FC



STATUS REPORT NO. 6

on

THE PHYSICAL AND CHEMICAL  
PROPERTIES OF TITANIUM BROMIDES  
AND TITANIUM IODIDES  
Contract No. Nonr-1120(00)

to

HEAD, METALLURGY BRANCH  
OFFICE OF NAVAL RESEARCH

July 1, 1955

by

J. M. Blocher, Jr., N. D. Veigel,  
E. H. Hall, and I. E. Campbell

BATTELLE MEMORIAL INSTITUTE  
505 King Avenue  
Columbus 1, Ohio

# Battelle Memorial Institute

5 0 5   K I N G   A V E N U E   C O L U M B U S   I ,   O H I O

July 29, 1955

Mr. W. C. Arsem  
Metallurgy Branch  
Office of Naval Research  
Department of the Navy  
Washington 25, D. C.

Dear Mr. Arsem:

Contract No. Nonr-1120(00)

Enclosed are two copies of Status Report No. 6 covering the period from April 1, 1955, to July 1, 1955.

Sincerely yours,



I. E. Campbell

IEC:mm  
Enc. (2)  
cc: See Distribution List

DISTRIBUTION LIST

Dr. O. T. Marzke  
Superintendent, Metallurgy Division  
Naval Research Laboratory  
Washington 25, D. C.

Col. B. S. Mesick  
Commanding Officer  
Watertown Arsenal  
Watertown 72, Massachusetts

Aeronautical Research Laboratory  
Wright Air Development Center  
Wright-Patterson Air Force Base, Ohio  
Attention WCRRL, J. G. Jackson ??

Office, Chief of Ordnance  
ORDTB-Materials  
Washington 25, D. C.  
Attention E. J. Dunn

ONR Resident Representative  
The Ohio State University  
Research Foundation Office Building  
Columbus 10, Ohio

ONR Branch Office  
The John Crerar Library Building  
86 East Randolph Street  
Chicago 1, Illinois

Dr. A. J. Stosick  
Jet Propulsion Laboratory  
California Institute of Technology  
Pasadena, California

Dr. C. J. B. Fincham  
Columbia University  
New York, New York

Dr. G. E. MacWood  
The Ohio State University  
Columbus, Ohio

Dr. F. D. Rossini  
Carnegie Institute of Technology  
Pittsburgh, Pennsylvania

Dr. R. Gilchrist  
Inorganic Chemistry Division  
National Bureau of Standards  
Washington 25, D. C.

Mr. E. J. Prosen  
Thermochemistry Division  
National Bureau of Standards  
Washington 25, D. C.

Dr. K. K. Kelley  
U. S. Department of the Interior  
Bureau of Mines  
126 Hearst Memorial Mining Building  
Berkeley, California

Dr. M. A. Steinberg  
Horizons, Incorporated  
Cleveland, Ohio

Dr. P. Herasymenko  
New York University  
College of Engineering  
Research Division  
University Heights  
New York 53, New York

Dr. R. S. Dean  
Chicago Development Company  
Riverdale, Maryland

Mr. A. D. Schwope  
Brush Laboratories Company  
540 East 105th Street  
Cleveland, Ohio

Mr. E. J. Chapin  
Department of the Navy  
Naval Research Laboratory  
Washington 25, D. C.

Dr. L. A. McClaine  
The Merrill Company  
(Arthur D. Little, Inc.)  
322 Battery Street  
San Francisco 11, California

Dr. G. F. Janz  
Rensselaer Polytechnic Institute  
Troy, New York

## TABLE OF CONTENTS

	<u>Page</u>
SUMMARY . . . . .	1
INTRODUCTION . . . . .	1
MERCURY REDUCTION OF TITANIUM TETRABROMIDE . . . . .	2
Experimental . . . . .	2
Discussion . . . . .	4
FUTURE WORK . . . . .	9

# THE PHYSICAL AND CHEMICAL PROPERTIES OF TITANIUM BROMIDES AND TITANIUM IODIDES

by

J. M. Blocher, Jr., N. D. Veigel,  
E. H. Hall, and I. E. Campbell



## SUMMARY

Data obtained in a study of the mercury reduction of titanium tetrabromide were used to calculate the difference in the heats of formation of  $\text{TiBr}_4(\text{s})$  and  $\text{TiBr}_3(\text{s})$ . After confirmation, these results will be combined with the heat of formation of  $\text{TiBr}_4(\text{s})$  now being determined at the National Bureau of Standards to obtain the value for the heat of formation of  $\text{TiBr}_3(\text{s})$ . Tentative values are included in this report.

Tests are being made of modifications of the apparatus for the determination of the disproportionation pressure of  $\text{TiBr}_3$  in order that reliable pressure-temperature-composition data can be obtained which will be combined with the above to give the heat of formation of  $\text{TiBr}_2(\text{s})$ .

## INTRODUCTION

As initially planned, the thermodynamic properties of the titanium bromides were to have been determined by studying the equilibria:



Acceptable values of the heat of formation of  $\text{Hg}_2\text{Br}_2$  were available\*, and exploratory work with the mercury-reduction reaction (Equation 1) indicated that reliable experimental results could be obtained.

The disproportionation of  $\text{TiBr}_3$  (Equation 2) had also been studied. However, this system is not "well behaved" and further work will be necessary to establish a reliable value of the heat of disproportionation.

\*Circular 500, National Bureau of Standards.

The disproportionation of  $\text{TiBr}_2$  (Equation 3) was to have been studied to complete the determination of the relative thermodynamic properties of the titanium bromides. However, this system would undoubtedly be still more difficult to work with than the tribromide disproportionation. Therefore, it was desirable that another reaction be chosen to complete the picture.

Fortunately, reliable values for the heat of formation of  $\text{TiBr}_4$  should result from the work in progress at the National Bureau of Standards by E. J. Prosen and his associates\*. With this information available, only the heats of reaction of Equations (1) and (2) will be necessary to determine the heats of formation of the three titanium bromides.

Details of recent work on the tribromide disproportionation were given in Status Report No. 5. During the present report period, tests were made of several techniques for obtaining reliable pressure-temperature-composition data. However, no experimental measurements were made. The major effort during the report period was concentrated on the determination of the equilibrium  $\text{TiBr}_4$  pressure in the mercury reduction reaction (Equation 1).

## MERCURY REDUCTION OF TITANIUM TETRABROMIDE

### Experimental

To identify the solid phases in equilibrium with liquid mercury and  $\text{TiBr}_4$  vapor, samples of the reaction product were subjected to X-ray-diffraction analysis at temperatures from  $150^\circ$  to  $250^\circ\text{C}$ . at which the equilibrium pressure of  $\text{TiBr}_4$  is easily measured.  $\text{TiBr}_3$  and  $\text{Hg}_2\text{Br}_2$  were identified as solid phases and no unidentified lines remained which might indicate complicating factors.

Measurements of the equilibrium pressure were made in the apparatus shown in Figure 1. The cell was carefully cleaned and outgassed and then charged with mercury by distillation from a reservoir attached at Point A. A small amount of pure  $\text{TiBr}_4$  was also distilled into the cell and allowed to react with the mercury to form a surface coating of  $\text{Hg}_2\text{Br}_2$  and  $\text{TiBr}_3$ , after which the cell was sealed off at A and separated from the filling apparatus. The purpose of the flexible rubber tubing connecting the cell to the vacuum and controlled-pressure system was to permit outgassing by inverting the cell and evacuating the system.

The cell was used as a null indicator, the pressure above the bromides being balanced by a measured pressure of inert gas which was varied until

---

\*Private communication, March 7, 1955.



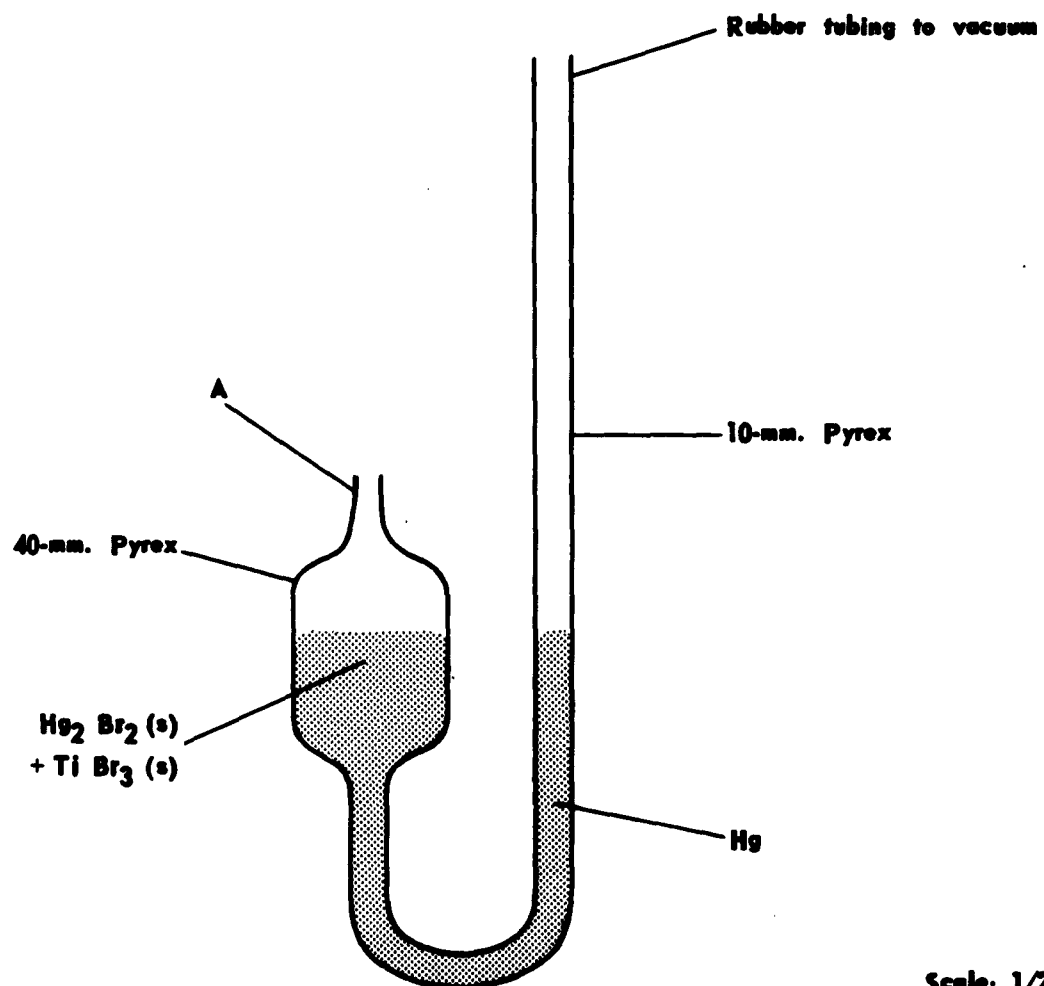


FIGURE 1. MERCURY REDUCTION CELL

the mercury level in the 10-mm tube was returned to the position occupied at zero pressure differential. Data for the correction for the thermal expansion of mercury were obtained with mercury alone in the cell by determining the mercury level in the 10-mm tubing as a function of temperature under zero pressure differential. As a check on the reliability of the technique, and of the prediction that the partial pressure of  $\text{HgBr}_2(\text{g})$  is negligible\*, the cell was charged with mercury and bromine to form a scum of  $\text{Hg}_2\text{Br}_2$  over the mercury surface. The pressure-temperature data given in Table 1 indicate that only the partial pressure of mercury is significant although there appears to be a small systematic error in the experimental values. This saturated mercury vapor pressure is exerted, along with the equilibrium  $\text{TiBr}_4$  pressure, in the mercury-reduction reaction, and must be subtracted from the total pressure to obtain the partial pressure of  $\text{TiBr}_4$ .

The cell was thermostatted to  $\pm 0.2^\circ\text{C}$ . in a salt bath whose temperature was measured by a calibrated Chromel-Alumel thermocouple. The data obtained with two separate preparations (Runs A and B) are given in Table 2 and Figure 2.

### Discussion

In order to extrapolate the experimental data to  $298.2^\circ\text{K}$ ., it is necessary to obtain a value for the  $\Delta C_p$  of reaction. Unfortunately, reliable values for the heat capacities of  $\text{TiBr}_3$  and  $\text{Hg}_2\text{Br}_2$  are not available. However, values obtained by estimation should be entirely satisfactory for this purpose. The heat capacity of  $\text{Hg}_2\text{Br}_2$  was taken as the average (24.8 cal./mole/deg. at  $298.2^\circ\text{K}$ .) of those of  $\text{Hg}_2\text{Cl}_2$  and  $\text{Hg}_2\text{I}_2$  given in National Bureau of Standards Circular 500. The heat capacity of  $\text{TiBr}_3$  (also 24.8 cal./mole/deg. at  $298.2^\circ\text{K}$ .) was estimated by adding 0.8 cal./deg./gram-atom to the heat capacity of  $\text{TiCl}_3$  obtained by averaging the heat capacities given for  $\text{VCl}_3$  and  $\text{AlCl}_3$ . The heat capacity of mercury is also given in Circular 500. That of  $\text{TiBr}_4(\text{g})$  was obtained by calculation from spectroscopic data as discussed previously\*\*. The resulting value of  $\Delta C_p = -6.5$  was taken to be constant over the temperature range of the measurements.

Owing to the uncertainty in the zero setting during Run A, together with the fact that the charge in the cell became depleted at higher temperatures, the values obtained in that run are shown only for purposes of indicating a rough check on the measurements of Run B. Treatment of the data from Run B gives, for Equation (1),

\*Calculations based on the data given by Brewer (National Nuclear Energy Series, Vol. IV-19B, McGraw-Hill, 1950) indicate a  $\text{HgBr}_2$  pressure, for example, of 0.13 mm. at  $225^\circ\text{C}$ .

\*\*Status Report No. 3, October 1, 1954, p. 10.

TABLE 1. TOTAL PRESSURE OVER  $\text{Hg}(\ell)$  AND  $\text{Hg}_2\text{Br}_2(\text{s})$ 

Temperature, °C.	$P_{\text{total}}^{(a)}$ mm. of Hg	$P_{\text{Hg}(\text{g})}^{(b)}$ mm. of Hg	$P_{\text{total}} - P_{\text{Hg}}$ mm. of Hg	$\frac{\Delta p}{p}$ , %
236.5	52.3	51.6	0.7	1.35
238.1	54.4	54.0	0.5	0.93
246.2	67.3	67.3	0.0	0.0
254.5	83.9	83.7	0.2	0.24
257.9	91.7	91.2	0.5	0.55
274.1	137.1	136.4	0.7	0.52

(a) Observed pressure corrected for latitude, and for thermal expansion of mercury in the cell and in the manometer.

(b) Handbook of Chemistry and Physics, 35th Edition, Chemical Rubber Publishing Company (1953-54), page 2147.

TABLE 2. EQUILIBRIUM  $\text{TiBr}_4$  PRESSURE IN MERCURY  
REDUCTION REACTION

Run(a)	Temperature, °K.	$\text{PTiBr}_4$ , mm. of Hg	$\Sigma$	-I
A	449.3	6.4	-	-
A	443.4	4.3	-	-
A	430.5	1.7	-	-
A	472.3	21.7	-	-
A	466.0	16.9	-	-
A	463.3	14.0	-	-
A	446.8	5.6	-	-
B	462.7	12.0	6.9166	91.4126
B	475.7	25.0	7.2745	91.4170
B	492.2	60.8	7.7089	91.4552
B	459.4	10.0	6.8272	91.4332
B	449.7	5.6	6.5450	91.4408
B	491.0	56.5	7.6738	91.4318
B	510.7	139.8	8.1253	91.3170
B	444.1	3.7	6.3474	91.3120
			Avg. = $\overline{91.4024}$ $\pm 0.052$	

(a) Data listed in order taken.

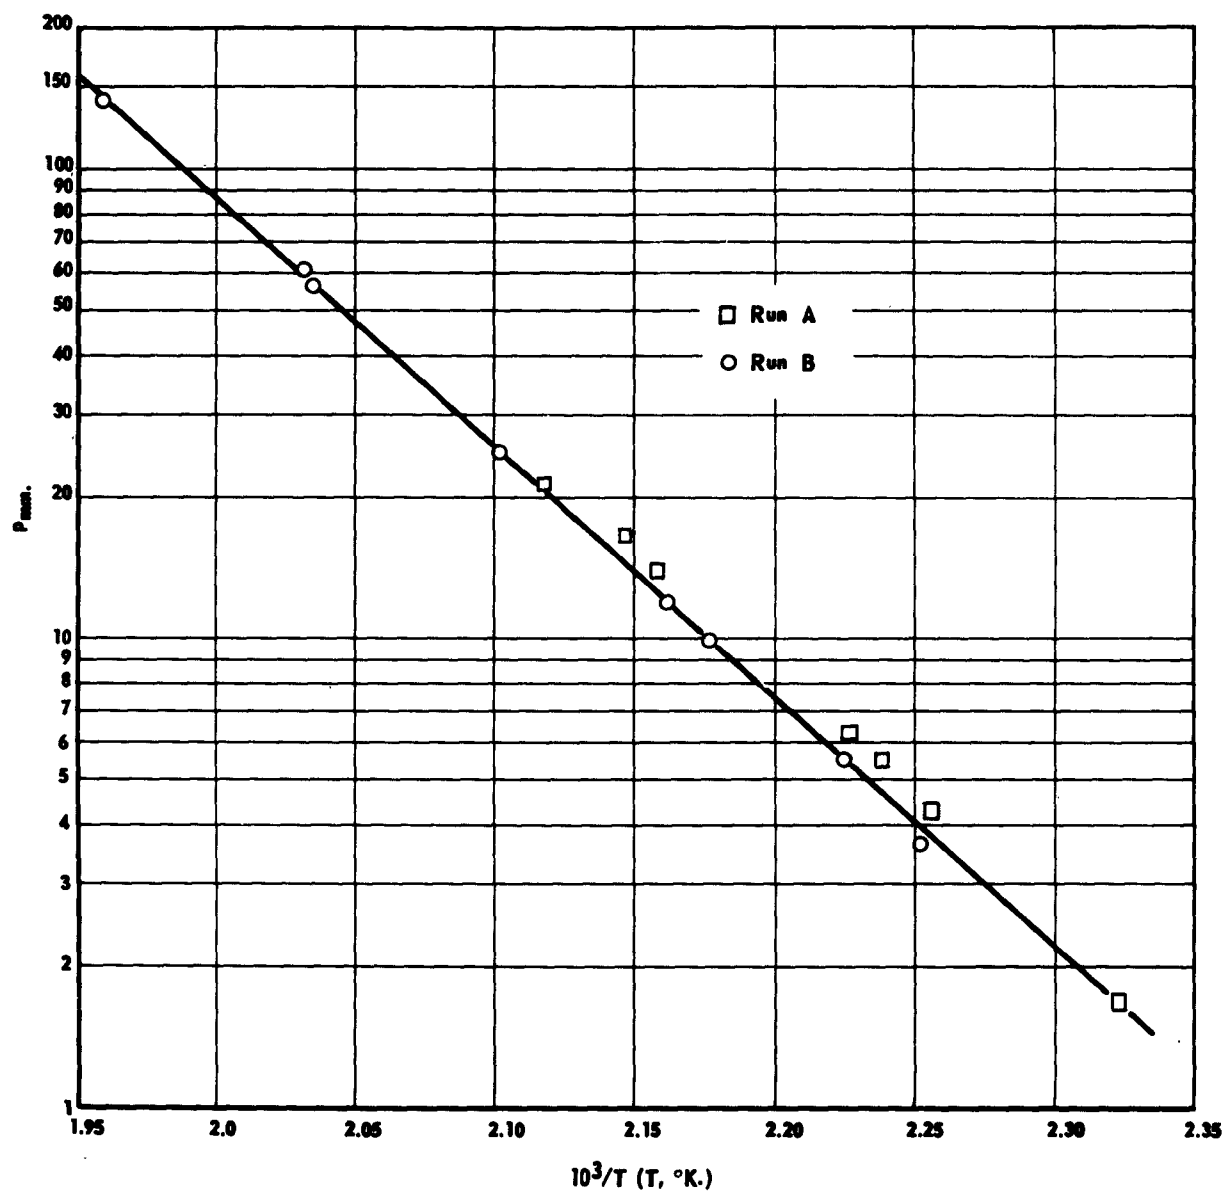


FIGURE 2. EQUILIBRIUM  $\text{TiBr}_4$  PRESSURE IN MERCURY REDUCTION REACTION

$$\log p_{\text{atm.}} = -6044.9/T - 3.271 \log T + 19.979$$

$$\Delta H_f^\circ = 27.66 \pm 0.21 \text{ kcal./mol}$$


$$\Delta H_{298.2} = 25.72 \pm 0.21 \text{ kcal./mol}$$

$$\Delta S_{298.2} = 47.86 \text{ e. u.}$$


Since entropy values can be estimated with much greater certainty than can heats of reaction, comparison of the entropy change obtained in the above work with that calculated from the best available information gives a good indication of the reliability of the experimental data. In calculating the entropy change for the reaction given by Equation (1), the values at 298.2°K. for Hg (l) = 18.5 e.u. and 1/2 Hg<sub>2</sub>Br<sub>2</sub>(s) = 25.45 e.u. were taken from Circular 500. The value for TiBr<sub>4</sub>(g) = 95.02 e.u. was calculated for spectroscopic data\*, and that for TiBr<sub>3</sub>(s) = 43 was taken from Brewer\*\*. The difference between the experimental value, ΔS<sub>298.2</sub> = 47.86 e.u., and the calculated value, 45.07, is well within the ± 7 e.u. uncertainty in the estimated entropy of TiBr<sub>3</sub>.

The internal consistency of the data is indicated by the small deviation in the I values given in Table 2.


The above results may be combined with the heat of formation of Hg<sub>2</sub>Br<sub>2</sub> (-49.42 kcal./mol.) and the heats of vaporization and fusion of TiBr<sub>4</sub> as determined at Battelle (13.02, and 3.06 kcal./mol., respectively, at 298.2\*\*\*) to yield, for the reaction



E. J. Prosen and his associates at the National Bureau of Standards have recently obtained\*\*\*\* for



This may be combined with the above data to give the heat of formation of TiBr<sub>3</sub>(s):



These results must be considered to be tentative, since additional measurements will be required to establish their precision. However, they are presented here with the thought that they may be useful to others.

\*Status Report No. 3, October 1, 1954, p. 10.

\*\*Brewer, loc. cit.

\*\*\*Status Report No. 3, October 1, 1954, p. 10.

\*\*\*\*Wagman, D. D., private communication, July 25, 1955.

FUTURE WORK

Additional data will be obtained for the equilibrium  $\text{TiBr}_4$  pressure in the mercury reduction reaction.

The equipment used to determine the disproportionation pressure of  $\text{TiBr}_3$  will be modified to obtain more reliable pressure-temperature-composition data.

Original data are contained in Battelle Laboratory Record Book No. 10105, pp. 51-75.

JMB:NDV:EHH:IEC/mm